

Cohesive modeling of dynamic fracture in reinforced concrete

Rena C. Yu*, Xiaoxin Zhang and Gonzalo Ruiz

*ETSI de Caminos, C.y P., Universidad de Castilla-La Mancha, 13071 Ciudad Real, Spain
(Received November 1, 2007, Accepted January 1, 2008)*

Abstract In this work we simulate explicitly the dynamic fracture propagation in reinforced concrete beams. In particular, adopting cohesive theories of fracture with the direct simulation of fracture and fragmentation, we represent the concrete matrix, the steel re-bars and the interface between the two materials explicitly. Therefore the crack nucleation within the concrete matrix, through and along the re-bars, the deterioration of the concrete-steel interface are modeled explicitly. The numerical simulations are validated against experiments of three-point-bend beams loaded dynamically under various strain rates. By extracting the crack-tip positions and the crack mouth opening displacement history, a two-stage crack propagation, marked by the attainment of the peak load, is observed. The first stage corresponds to the stable crack advance, the second one, the unstable collapse of the beam.

Keywords: dynamic fracture; cohesive elements; crack propagation time.

1. Introduction

Many phenomenological models have been developed to study the problem of complex fracture processes in reinforced concrete specimens, in particular, when the propagation is static (Bosco and Carpinteri (1992), Ruiz, *et al.* (1999), Ruiz (2001), Ruiz, *et al.* (2006)). Those models focus on a crack that propagates through a reinforcement layer and that, at opening, causes the steel bars to be pulled-out. The main difficulty consists in modeling the propagation of the crack through the reinforcement layer, as such a layer in 2D models constitutes a discontinuity that stops the crack advance. Modeling the steel-concrete interaction is not simple either, since the pull-out process produces damage at the interface and it may also generate secondary fracture processes within the concrete bulk. Some of the aforementioned models solve both problems by substituting the re-bars for closing forces applied at the crack lips; whose intensity relates to the strength of the reinforcement and of the interface (Heddal and Kroon 1991, Brincker, *et al.* 1999). Some authors model the steel bars explicitly, however they only account for the extreme cases of perfect or null adherence (Hawkins and Hjørsetet 1992). Ruiz, *et al.* (2006) developed a simplified model that enables propagation of the crack through the reinforcement as well as interface deterioration. They adopted a computational strategy that consisted of overlapping both materials in the same spatial position. Concrete was modeled as a continuum, whereas steel was overlapped and connected by interface elements to nodes occupying the same initial position (Hawkins and Hjørsetet 2004). Concrete continuity allowed crack propagation through the reinforcement and interface elements

* Corresponding author, Email: rena@uclm.es

transmitted shear stresses depending on the relative displacement between the two materials. However, their numerical model was not able to reproduce micro-cracking and/or damage around the main crack (Ruiz 2001) and along the steel-concrete interface (Ben Romdhane and Ulm 2002).

In dynamic regime, the fracture processes in reinforced concrete beams are more complicated than in the static case, as stress waves can be partly included from the steel-concrete interface and partly transmitted to the re-bar. The interplay between the interface, steel re-bar and concrete matrix challenges the above numerical models, in which either the re-bar is not physically represented (Heddal and Kroon 1991, Brincker, *et al.* 1999, Ruiz, *et al.* 2006), or the progressing deterioration of the interface is not included (Hawkins and Hjørsetet 1992). Indeed, such an interaction calls for an explicit modeling of those phenomena.

In this work, following previous efforts in explicitly modeling in static regime (Yu and Ruiz 2006), we attempt to simulate explicitly the dynamic fracture propagation in reinforced concrete beams. In particular, adopting cohesive theories of fracture with the direct simulation of fracture and fragmentation (Ortiz and Pandolfi 1999, Pandolfi and Ortiz 2002), we represent the concrete matrix, the steel re-bars and the interface between the two materials explicitly. Therefore the crack nucleation within the concrete matrix, through and along the re-bars, the deterioration of the concrete-steel interface are modeled explicitly. The organization of this paper is as follows. In the next section, the experimental setup is illustrated followed by the description of material characterization. A brief description of the cohesive model is provided in Section 4. In Section 5, the simulation results are discussed and finally, in Section 6, the work is summarized and some conclusions are drawn.

2. Experimental setup

Zhang *et al.* (2008) conducted a series of tests in order to study the combined size and strain rate effect in lightly reinforced concrete beams. The loading rate ranged from 10^{-5} to 10^{-2} /s for beams of three sizes. The tests were carried out in a three-point-bend configuration as shown in Fig. 1, where the width B is 50 mm, the depth D is 75 mm, 150 mm and 300 mm for small, medium and large specimens respectively. The specimens were casted to give a constant steel-reinforcement ratio of 0.15%. Fig. 2 shows the experimental set-up for three-point bending tests. The specimen rests on two rigid-steel cylinders laid on two supports permitting rotation out of the plane of the beam and rolling along the beam longitudinal axis with negligible friction. These supports roll on the upper surface of a very stiff beam fastened to the machine actuator. The load-point displacement is measured in relation to points over the supports on the upper surface of the beam. Two LVDT (linear variable differential transducer) fixed on the steel beam are directly used to measure the

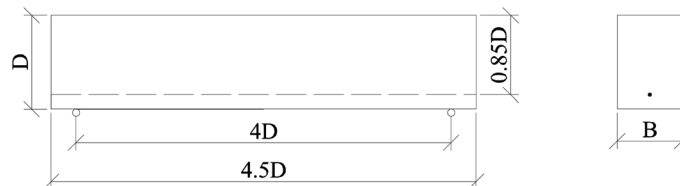


Fig. 1 A reinforced concrete beam subjected to three point bending

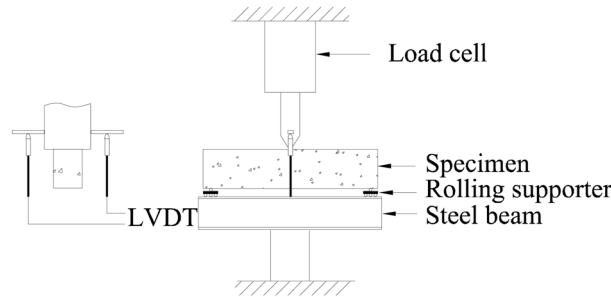


Fig. 2 Experimental set-up for three-point bending tests on beams

displacement between the loading rod and the steel beam. For loading, a hydraulic servo-controlled test system was employed. The tests were performed in position-control. In numerical simulation, we take the experimental results for small specimens at a loading velocity of 7.5 mm/s as comparison. The strain rate at the bottom surface is related to this loading velocity through

$$V = \dot{\delta} = \dot{\epsilon} S^2 / 6D \quad (1)$$

where S and D are the span and depth of the beam, respectively, δ is the loading point displacement.

3. Material characterization

A single micro-concrete was used throughout the experiment made with lime aggregates of 5 mm aggregate size and ASTM type II/A cement. The mix weight proportions were 3.2:0.5:1 for aggregate:water:cement conforming to ASTM C33. Table 1 shows the characteristic mechanical parameters of the micro-concrete determined in the various characterization and control tests, where f_c , f_t , E_c , G_F , ρ , are the compressive strength, tensile strength, elastic modulus, fracture energy, and mass density, respectively. The Hillerborg's characteristic length, calculated as $l_{ch} = E_c G_F / f_t^2$, is around 105 mm.

The mechanical properties of the steel, the elastic modulus E_s , the standard yield strength the $\sigma_{0.2}$, the ultimate strength σ_u and strain ϵ_u as well as the bond strength τ_c between the concrete and the re-bar are all shown in Table 2.

Table 1 Micro-concrete mechanical properties

f_t MPa	f_c MPa	E_c GPa	G_F N/m	ρ kg/m
3.74	28.4	29.6	49.5	2113

Table 2 Mechanical properties of the steel re-bar and the interface bond strength

E_s GPa	$\sigma_{0.2}$ MPa	σ_u MPa	ϵ_u	τ_c MPa
133.2	434.1	465.1	0.9%	5.3

4. Numerical model

We briefly summarize here the cohesive model adopted for the concrete matrix, further information can be found elsewhere and the references within (Ortiz and Pandolfi 1999, Ruiz, *et al.* 2000, 2001). A variety of mixed-mode cohesive laws accounting for tension-shear coupling (Camacho and Ortiz 1996, Ortiz and Pandolfi 1999, De Andrés, *et al.* 1999), are established by the introduction of an effective opening displacement δ ,

$$\delta = \sqrt{\beta^2 \delta_s^2 + \delta_n^2} \quad (2)$$

which assigns different weights to the normal δ_n and sliding δ_s opening displacements. Supposing that the cohesive free-energy density depends on the opening displacements only through the effective opening displacement δ , a reduced cohesive law, which relates δ to an effective cohesive traction t , can be obtained (Camacho and Ortiz 1996, Ortiz and Pandolfi 1999). The resulting traction vector that unites the two faces of the cohesive crack is

$$\mathbf{t} = (\beta^2 \delta_s + \delta_n \mathbf{n}) t / \delta \quad (3)$$

where t , the effective cohesive traction, is

$$t = \sqrt{\beta^2 t_s^2 + t_n^2} \quad (4)$$

t_s and t_n being the shear and the normal components of \mathbf{t} respectively. The weighting coefficient β is considered a material parameter that measures the relation between the shear and tensile resistance of the material, it is taken as 5 for plain concrete following the study of Ruiz, *et al.* (2001). The existence of a loading envelope defining a connection between t and δ under the conditions of monotonic loading, and irreversible unloading is assumed. A linear decreasing cohesive law is adopted in the calculations.

A damage variable d , is defined as the fraction of the expended fracture energy over the total fracture energy per unit surface. Thus, a damage value of zero denotes an intact surface, whereas a damage value of one is indicative of a fully cracked or free surface.

The cohesive model introduces an intrinsic time described by

$$t_{ch} = \frac{\rho c \delta_c}{2f_t} \quad (5)$$

where ρ represents the mass density, c , the longitudinal wave velocity, δ_c , the critical opening displacement. As shown in Ruiz, *et al.* (2001), Yu, *et al.* (2004), due to this intrinsic time, the cohesive model is able to respond differently for a slow and fast loading process. For the material properties given in Table 1, t_{ch} is calculated as 28 μ s.

In treating the steel-concrete interface, we follow the methodology illustrated in Yu and Ruiz (2006). A cohesive-like interface element is implemented. This interface element is inserted only when the slip strength is attained. The sliding between two surfaces is governed by a perfect-plastic bond-slip law. The steel re-bar is modeled as an elastic-perfectly plastic material, the concrete bulk is simply taken as a rate-independent elastic material.

Explicit Newmark central integration is adopted, a stable time step of 0.01 μ s is used for all the calculations and the computation is stopped shortly after the main crack reaches the top surface of the beam.

5. Numerical results

We chose to model the small beam, 75 mm in depth to compare with the experimental results. The initial mesh consists of 6764 quadratic tetrahedrons and 10142 nodes, see Fig. 3. The mesh size near the middle surface, 7 mm, is chosen to be comparable to the maximum aggregate size, 5 mm, based on the convergence analysis done by Ruiz, *et al.* (2000, 2001) in modeling plain concrete in a dynamic regime. The mesh size in concrete bulk varies by a factor of four, which guarantees that spurious wave effects are not being introduced. This has been shown in Ruiz, *et al.* (2001). The average mesh size that resolves the interface—around 10 mm—is designed to resolve the effective slip length L_s , which can be described as

$$L_s = A_s f_y / \tau_c p \quad (6)$$

according to Ruiz (2001), where f_y is the yield strength, A_s is the steel cross-section area, p the rebar perimeter, τ_c the interface bond strength. L_s is computed as 54.3 mm.

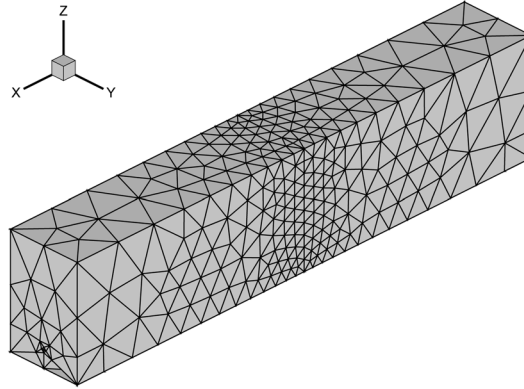


Fig. 3 The initial mesh

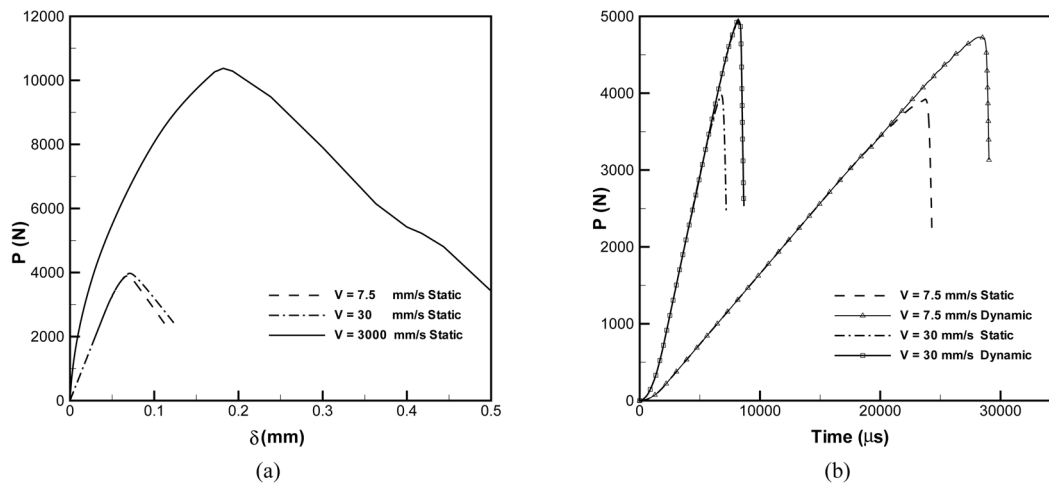


Fig. 4 (a) Numerical load-displacement curves for loading velocities of 7.5, 30 and 3000 mm/s, applying static fracture properties (G_F , and τ_c). (b) Comparison of numerical loading displacement curves obtained using static and dynamic fracture properties

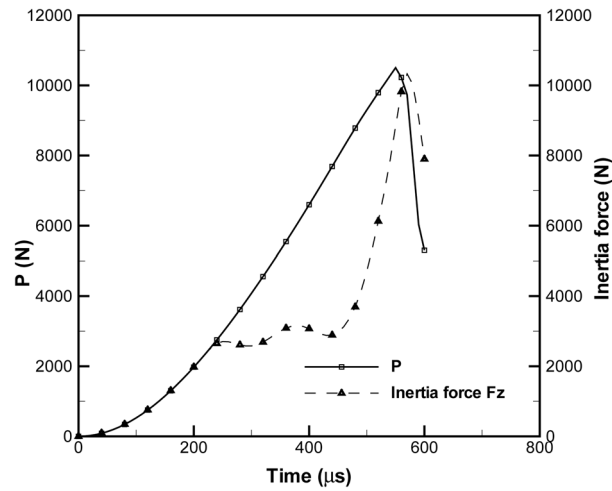


Fig. 5 Comparison of load P and the amplitude of inertia force in the vertical direction for loading velocity of 3000 mm/s

We load the beam through an elastic spring to reflect the fact that in the experiments the load transfer is realized through a mechanical system (loading rod, reaction frame, etc.), whose stiffness is 38 kN/mm.

As mentioned in Section 2, we are going to simulate the experimental results obtained for the loading velocity of 7.5 mm/s. We additionally performed numerical simulations for loading velocities of 30 and 3000 mm/s to study the sensitivity of the model to changes in the loading rate.

5.1. Peak load

The first step of the simulations was to check the predicted peak load. As we mentioned before, we expected the cohesive model to respond to the dynamic loading. As the strain rate increases, the predicted peak loads should increase accordingly. But as can be seen from Fig. 4(a), when the loading velocity is increased from 7.5 mm/s to 30 mm/s, the peak load is practically the same, while when we prescribed a loading velocity of 3000 mm/s, the peak load increased from 4 kN to 10 kN. If we define t_p , the crack propagation time as the time interval between crack initiation and the attainment of peak load, t_p is about 7000, 3000 and 80 μ s for loading velocities of 7.5 mm/s, 30 mm/s and 3000 mm/s respectively, see Fig. 7. This shows that when t_p is not comparable to the intrinsic time t_{ch} of the cohesive model (28 μ s), the strength increase cannot be captured.

This also confirms the observations of Rossi and Toulemonde (1996). They pointed out that, at strain rates smaller than approximately 1/s, –loading velocity of 7.5 mm/s corresponds to a loading rate of 0.375/s–, the moisture content is believed to play an important role in the strength increase of concrete, the free water in the micro-pores exhibits the so-called Stephan effect causing a strengthening in concrete with increasing loading rate. The Stephan effect counters both a micro-cracking localization, leading to increase of concrete tensile strength, and the macro crack propagation that leads to failure of the specimen. Rossi and Toulemonde also showed that at strain rates higher than or equal to 10/s, –loading velocity of 3000 mm/s represents 15/s in our case–, the micro-inertia effects in the fracture process zone might cause the rate dependence of concrete,

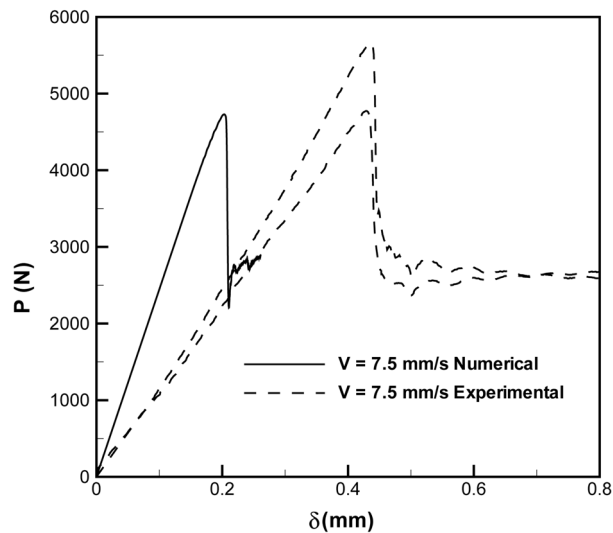


Fig. 6 Numerical (using dynamic fracture properties) and experimental load-displacement comparison for loading velocity of 7.5 mm/s

whereas the moisture content is assumed not to be dominant. The inertia counters micro-cracking localization and in particular macro-crack propagation.

In order to capture the strength increase due to moisture content, which is not covered by the bulk constitutive law, we fit for the experimental data of Harsh, *et al.* (1990) to obtain a 30% increase for the fracture energy and the tensile strength in the case of loading velocity of 7.5 mm/s, the strength of the interface was also increased in the same proportion. This gives us a peak load of 4.8 kN, comparable to the experimental data 5.22 kN, the average peak-load of two specimens, see Fig. 6. Note that we didn't tailor the material parameter to make the numerical simulation to fit the experiments, but followed an independent source that gives the rate-dependent material properties. For the case of 30 mm/s, which represents a loading rate of 1.5/s, the fracture properties for the concrete bulk and the interface are increased a 38% by extrapolating the experimental results of Harsh, *et al.* (1990). As can be seen from Fig. 4(b), the peak load attained is about 4.95 kN, only a 3% increase compared to that of 7.5 mm/s, whereas a greater percentage of increase –around 23%– is expected according to the experimental results of Zhang, *et al.* (2008). We are currently implementing a viscous cohesive model (Ruiz, *et al.* (2008)) to better capture the fracture behavior in the loading rate between 1/s to 10/s, where the competition of Stephen effect, micro-crack localization and macro-crack propagation is particularly strong. For the case of 3000 mm/s, inertia forces are expected to play a dominant role, we simply adopt the static fracture properties in the calculations. This is confirmed by comparing the global load P and the amplitude of inertia force in the vertical direction, as shown in Fig. 5. For the case of 7.5 and 30 mm/s, the inertia force remained almost zero until reaching the peak load.

5.2. Initial stiffness

We observe in Fig. 6 that there is a difference in the initial stiffness between the two experimental curves, this has been explained by Planas, *et al.* (1992), who pointed out that even in the case of

identical beams made of the same material, the initial slopes may show variations. This is due to the sensitivity of the elastic exibility of the beam to the boundary conditions in the application of the concentrated load. Having in mind that, on the one hand, we would not know the exact experimental boundary condition but only the average, on the other hand the numerical discretization also introduces a predefined stiffness, this would all contribute to the deviation of the initial stiffness of the P - δ curve. But we want to emphasize that the post-peak behavior, for both the two experimental data and the numerical simulation, shows similarity. This gives us confidence for the succeeding analysis in extracting the crack tip velocities and the CMOD history.

5.3. Crack tip velocities

The crack tip positions for three different loading velocities, 7.5 mm/s, 30 mm/s and 3000 mm/s are plotted against time in Fig. 7. The crack tip positions at the central cross section of the beam were measured separately at the two vertical edges (solid line) and at the center (dashed line) from the bottom of the specimen. The crack tip position is measured with respect to the damage variable value of 0.05 in all the cases. In addition, the axes of the graphs in the proceeding figures have

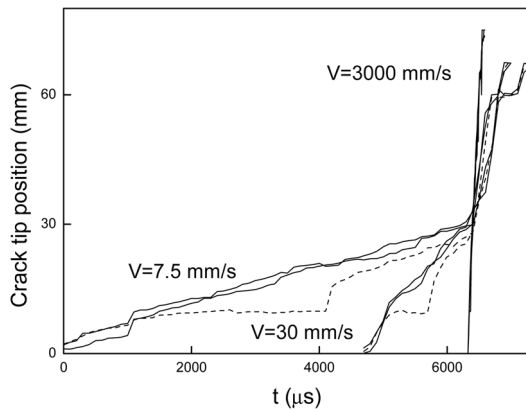


Fig. 7 Calculated crack tip position versus time for loading velocity at 7.5, 30 and 3000 mm/s respectively, where the solid lines correspond to values measured at specimen surface, dotted lines represent values measured at specimen center

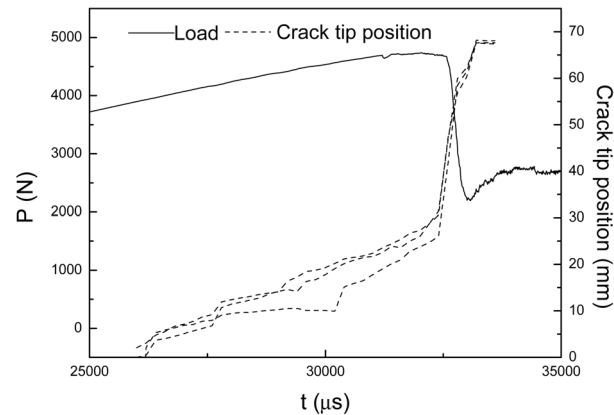


Fig. 8 Zoomed view of the numerical load history plotted against the computed crack tip position history for loading velocity of 7.5 mm/s

Table 3 Crack tip velocity (m/s)

	Loading velocity		
	7.5	30	3000
(Measured at surfaces)			
Pre-peak	3.9	15.6	290
Post-peak	70.5	95.4	280.5
(Measured at center)			
Pre-peak	3.5	14.8	296
Post-peak (mm/s)	75.7	112.4	289

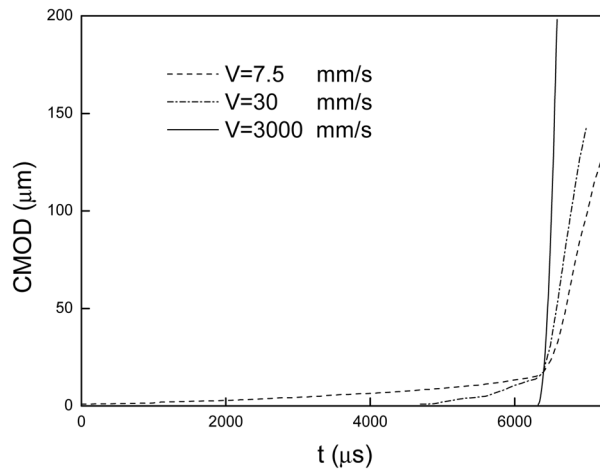


Fig. 9 Numerical CMOD history at 7.5, 30 and 3000 mm/s respectively

Table 4 CMOD rate (m/s)

	Loading velocity (mm/s)		
	7.5	30	3000
Pre-peak	0.002	0.0094	0.17
Post-peak	0.13	0.242	1.26

been adjusted to make the comparison easier. For loading velocities 7.5 mm/s and 30 mm/s, the crack velocities at the edges are approximately the same, showing a symmetric crack propagation with respect to the central line. The crack tip position at the center exhibits a plateau due to the hindrance of the steel re-bar. The initial slopes of the curves show a linear dependence on the loading velocity. For example, as shown in Table 3, the initial slopes for 7.5 and 30 mm/s are 3.5 m/s and 14.8 m/s respectively. A change in slope is observed at the peak load after which the new slope shows a marked similarity in both the cases. For loading velocity of 3000 mm/s, the slope of the curve is steep since the loading velocity is faster and the run completes in a shorter time span. In short, it is evident that crack tip velocity is close after the peak load is reached and it does not depend very much on the loading velocity. The second slope for loading velocity of 7.5 mm/s is about 20 times larger than its first slope, while for 30 mm/s is about 10 times larger. We can say that the crack went through a stable-to-unstable transition when the loading velocity is relatively low. However, at higher loading rate, the whole process is unstable.

In addition, in Fig. 8 we plot the load history around the peak load, against the crack tip position history for loading velocity of 7.5 mm/s. It shows that the main crack initiated around 80% (3800 N) of the maximum load (4800 N), and the attainment of the peak load marks the turning point of the two-stage crack propagation.

5.4. CMOD history

The crack mouth opening displacements for loading velocities, $v = 7.5, 30, 3000$ mm/s were obtained numerically at the central line of the bottom surface of the beam. The CMOD curves for

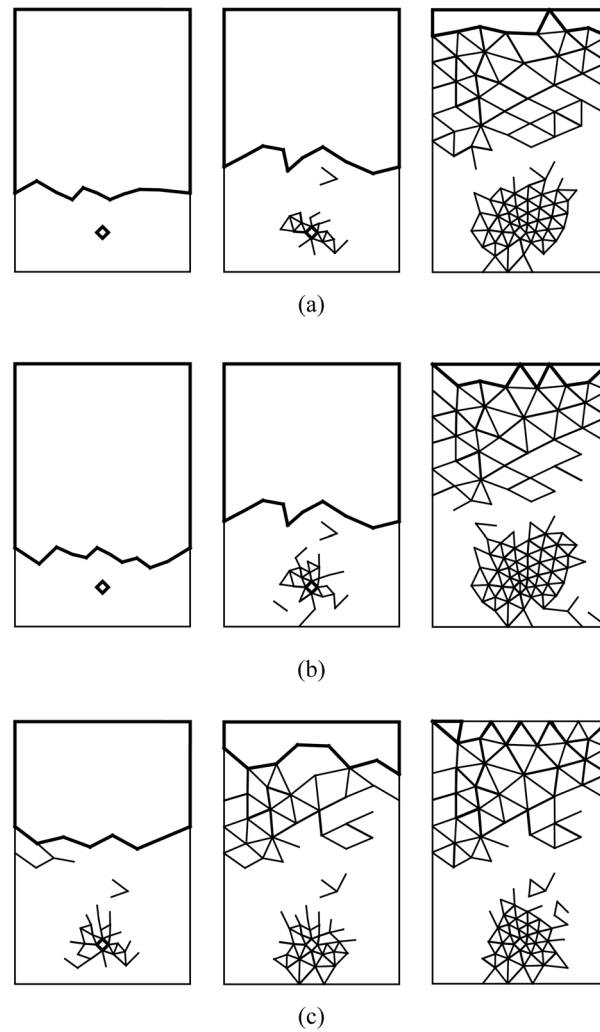


Fig. 10 The main crack front advancing and micro-crack formation for loading velocities of (a) 7.5, (b) 30, and (c) 3000 mm/s.

aforementioned velocities are plotted in Fig. 9. The curves exhibit a similar trend for all the loading velocities. They consist of two sections with different and approximately linear slopes; let us call them as the first and the second slope, the turning point is in correspondence with the time of reaching peak load. The detailed information is shown in Table 4. For loading velocity $v=7.5$ and 30 mm/s, the first slope changes by approximately the same factor by which the velocities are scaled; after the peak load, the CMOD rate is suddenly increased by around two orders of magnitude compared with that before peak load. This also means that the crack propagation shows a transition from stable to unstable state. While for loading velocity of 3000 mm/s, the CMOD rate before the peak load and after the peak load is similar, the whole crack propagation is unstable. As seen earlier, this trend is similar as compared to the crack tip position curves (Fig. 7).

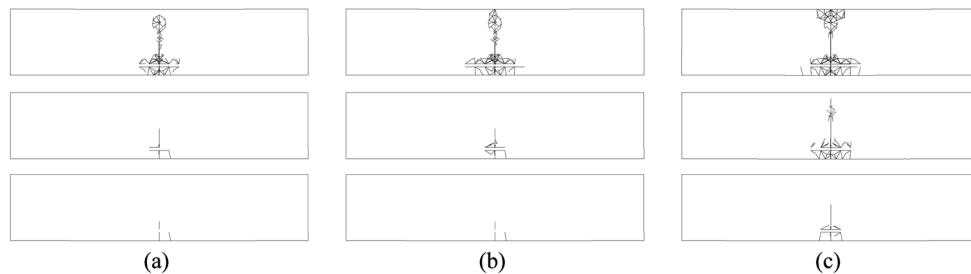


Fig. 10 The main crack front advancing and micro-crack formation for loading velocities of (a) 7.5, (b) 30, and (c) 3000 mm/s

5.5. Crack patterns

We paid close attention to the crack patterns of the reinforced beams at three characteristic point of the loading process: the intermediate time between the time of crack initiation and the time of reaching the peak load, the time of reaching the peak load and the time of breaking the beam. These patterns are illustrated from the loading plane (middle surface), as shown in Fig. 10. It shows that the crack patterns are similar for the two smaller loading velocities, whereas for 3000 mm/s, the crack is noticeably more advanced. In Fig. 11, we give the crack patterns observed from the vertical plane that passes the centroid line of the re-bar for the three loading velocities. Notice that micro-cracks have formed at the bottom surface and around the re-bar. The competition between micro-crack localization and macro-crack propagation is particularly strong around the re-bar and when the beam is about to break.

Acknowledgments

We would like to acknowledge the nancial support from the *Dirección*, Spain, on *General de Investigación* through Grants MAT2003-00843 and MAT2006-09105.

References

- Ben Romdhane, M. R. and Ulm, D. R. (2002), "Computational mechanics of the steel-concrete interface", *Int. J. Numer. Anal. Meth. Geomech.* **26**, 99-120.
- Bosco, C. and Carpinteri, A. (1992), "Fracture behaviour of beam cracked across reinforcement", *Theort. Appl. Fract. Mech.* **17**, 61-68.
- Brincker, R., Henriksen, M. S., Christensen, F. A. and Heshe, G. (1999), *Size effects on the bending behaviour of reinforced concrete beams.*, pp 127-180, Elsevier, London.
- Camacho, G. T. and Ortiz, M. (1996), "Computational modelling of impact damage in brittle materials", *Int. J. Solids Structs.* **33**(20-22), 2899-2938.
- De Andrés, A., Pérez, J. L., and Ortiz, M. (1999), "Elastoplastic finite-element analysis of three-dimensional fatigue crack growth in aluminum shafts subjected to axial loading", *Int. J. Solids Structs.* **36**(15), 2231-2258.
- Harsh, S., Shen, Z. J. and Darwin, D. (1990), "Strain-rate sensitive behavior of cement paste and mortar in compression", *ACI Mater. J.* **87**(6), 508-516.

- Hawkins, N. M. and Hjørsetet, K. (1992), *Minimum Reinforcement Requirement for Concrete Exural Members.*, pp 379-412, Elsevier, London.
- Hawkins, N. M. and Hjørsetet, K. (2004), *Bond of RC Members Using Nonlinear 3D FE Analysis*, pp 861-868, IA-FraMCoS.
- Heddal, O. and Kroon, I. B. (1991), "Lightly reinforced high-strength concrete", M. Sc. Thesis, University of Aalborg, Denmark.
- Ortiz, M. and Pandolfi, A. (1999), "Finite-deformation irreversible cohesive elements for three-dimensional crack-propagation analysis", *Int. J. Numer Meth. Eng.* **44**, 1267-1282.
- Pandolfi, A. and Ortiz, M. (2002), "An efficient adaptive procedure for three-dimensional fragmentation simulations", *Eng. Comput* **18**(2), 148-159.
- Planas, J., Guinea, G. and Elices, M. (1992), "Stiffness associated with quasi-concentrated load", *Mater. Structs.* **27**, 311-318.
- Rossi, P. and Toulemonde, E. (1996), "Effect of loading rate on the tensile behavior of concrete: description of the physical mechanisms", *Mater. Structs.* **29**(186), 116-118.
- Ruiz, G. (2001), "Propagation of a cohesive crack crossing a reinforcement layer", *Int. J. Fract.* **111**, 265-282.
- Ruiz, G., Carmona, J. R. and Cedón, D. A. (2006), "Local fracture and steel-concrete decohesion phe nomena studied by means of cohesive interface elements", *Comput Methods Appl. Mech. Eng.* **195**, 7237-7248.
- Ruiz, G., Elices, M. and Planas, J. (1999), "Size effect and bond-slip dependence of lightly reinforced concrete beams", *Minimum Reinforcement in Concrete Beams, ESIS Publications*, **24**, 67-98.
- Ruiz, G., Ortiz, M. and Pandolfi, A. (2000), "Three-dimensional nite-element simulation of the dynamic Brazilian tests on concrete cylinders", *Int. J. Numer Meth. Eng.* **48**, 963-994.
- Ruiz, G., Pandolfi, A. and Ortiz, M. (2001), "Three-dimensional cohesive modeling of dynamic mixed-mode fracture", *Int. J. Num. Meth. Eng.* **52**, 97-120.
- Ruiz, G., Zhang, X. X., Del Viso, J. R., Yu, R. C. and Carmona, J. R. (2008), "Loading rate effect on the fracture behavior of high strength concrete", *Cement Concrete Res.*, submitted.
- Yu, R. C. and Ruiz, G. (2006), "Explicit finite element modeling of static crack propagation in reinforced concrete", *Int. J. Fracture* **141**, 357-372.
- Yu, R. C., Ruiz, G. and Pandolfi, A. (2004), "Numerical investigation on the dynamic behavior of advanced ceramics", *Eng. Fract. Mech.* **71**, 897-911.
- Zhang, X. X., Ruiz, G. and Yu, R. C. (2008), "Experimental study of combined size and strain rate and size effects on the fracture of reinforced concrete", *J. Mater. Civ. Eng.*, accepted.